

Effect of stripe order strength for the Nernst effect in $\text{La}_{2-x}\text{Sr}_x\text{CuO}_4$ single crystals

T. Fujii^a, T. Matsushima^b, T. Maruoka^b, A. Asamitsu^{a,b}

^aCryogenic Research Center, University of Tokyo, Tokyo, 113-0032, Japan

^bDepartment of Applied Physics, University of Tokyo, Tokyo, 113-8656, Japan

Abstract

We have precisely measured the Nernst effect in Nd-doped $\text{La}_{2-x}\text{Sr}_x\text{CuO}_4$ single crystals with controlling the strength (stability) of the stripe order. We found that the onset temperature T_{onset} , where the Nernst signal starts increasing, does not change conspicuously in spite of Nd-doping. At low temperatures, on the other hand, the absolute value of the Nernst signal is strongly suppressed in accordance with the strength of the stripe order. These results imply that the fluctuation of (charge) stripe order enhances the Nernst signal below T_{onset} at high temperatures, and then the stripe order enhanced by Nd-doping suppresses the superconducting fluctuation to reduce the Nernst signal at low temperatures. We also observed an increase of the Nernst signal below the charge order temperature T_{ch} which is observed in diffraction measurement.

Key words: Nernst effect, vortex flow, stripe order

PACS: 74.25.Fy, 74.72.Dn, 74.62.Dh

1. Introduction

The Nernst effect in the normal state of high- T_c cuprates has become a focus of renewed attention since the detection of an anomalous Nernst signal in the normal state of underdoped cuprates [1]. It is widely accepted that the large Nernst signal is attributed to the movement of vortices which survives far above T_c . On the other hand, a large negative Nernst coefficient, which is comparable to the vortex signal in the superconducting state, has been reported in the charge density wave state of NbSe_2 [2]. Recently, it is reported that the stripe order causes the Nernst signal to become large in Nd or Eu doped $\text{La}_{2-x}\text{Sr}_x\text{CuO}_4$ [3]. Thus, two mechanisms for the origin of Nernst effect have been discussed up to now. The former supports the scenario that the superconducting gap opens far above T_c , although the long-range phase coherence is destroyed by vortex excitation. While the latter implies that the superconductivity occurs near the quantum critical point where the competing orders, such as stripe order and/or charge order, cross in the phase diagram. Here, to investigate the effects of the charge (stripe) ordered state on Nernst signal, we controlled the strength (stability)

of the stripe order by introducing Nd in $\text{La}_{2-x}\text{Sr}_x\text{CuO}_4$, and measured the Nernst effect.

2. Experimental

The high-quality single crystals of $\text{La}_{1.85-y}\text{Nd}_y\text{Sr}_{0.15}\text{CuO}_4$ ($y=0, 0.2$, and 0.4) were grown using the Traveling Solvent Floating Zone method. Grown boules were carefully cut into rectangular shape confirming the crystal axis by using X-ray laue camera. All samples were carefully prepared to have the same doping level by fixing the Sr content ($x=0.15$) and the doping level was confirmed by the absolute values of the thermopower at room temperature. T_c 's determined by susceptibility were 37K, 23K, and 12K for $y=0, 0.2$, and 0.4 respectively. For the samples of $y=0.2$ and 0.4 , we observed an upturn in the resistivities around 50K and 70K, respectively, at which charge order has been observed [4]. Nernst signal e_y , which is defined as the transverse electric field E_y per unit temperature-gradient ($e_y(H, T) = E_y/\nabla T$), was measured with applying three different temperature-gradients ($\nabla T \approx 0.5, 0.75, 1\text{K/mm}$). Temperatures and magnetic fields were stabilized during the measurement.

URL: fujii@crc.u-tokyo.ac.jp (T. Fujii)

Preprint submitted to Physica C

December 1, 2009

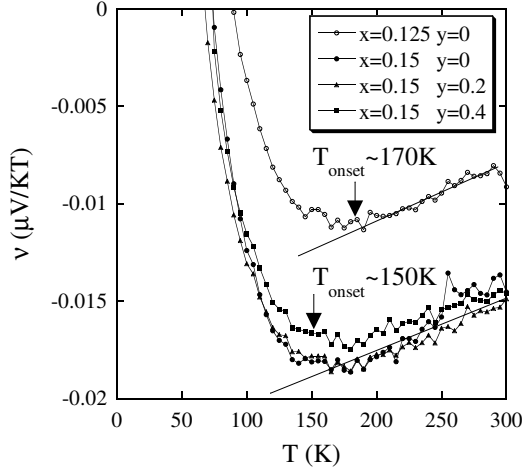


Figure 1: Nernst coefficient ν of $\text{La}_{2-x-y}\text{Nd}_y\text{Sr}_x\text{CuO}_4$ in high temperature.

3. Results and Discussion

Since the Nernst signal at high temperature is linear to magnetic field, we can define the Nernst coefficient ν as $e_y(H, T)/B$, where $B = \mu_0 H$. Figure 1 shows the temperature dependence of ν in high temperature. To clarify the doping dependence, ν of Nd-free sample with $x=0.125$ is also plotted. Note that the full scale of the vertical axis is as small as 20 nV/KT, which assures that the resolution of the measurement is better than 5 nV/KT. As seen in the figure, ν 's of $x=0.15$ are completely coincide irrespective of Nd content. The magnitude of ν is almost consistent with the previous report [1]. These results suggest that the absolute value of ν at high temperatures is determined only by the doping level x . More interestingly, the onset temperature T_{onset} , below which ν starts to deviate from high-temperature T -linear behavior (normal-term Nernst coefficient), does not change with Nd-doping, even though the superconducting transition temperature T_c is drastically reduced.

To investigate the effect of the stripe order, we show the temperature dependence of e_y at 9T in Fig. 2. The magnitude of e_y drastically decreases with Nd-doping below the temperature T_B , where the magnetic field dependence of the Nernst coefficient was observed (T_B was determined as ref.[3]). This result indicates that the fluctuation of superconductivity is suppressed by the stabilization of the stripe order due to Nd-doping below T_B . As seen in $\text{La}_{1.8-x}\text{Eu}_{0.2}\text{Sr}_x\text{CuO}_4$ of ref.[3], we observed the evolution of two-peak structure in the sample of $x=0.4$. Furthermore, an upturn of the Nernst signal

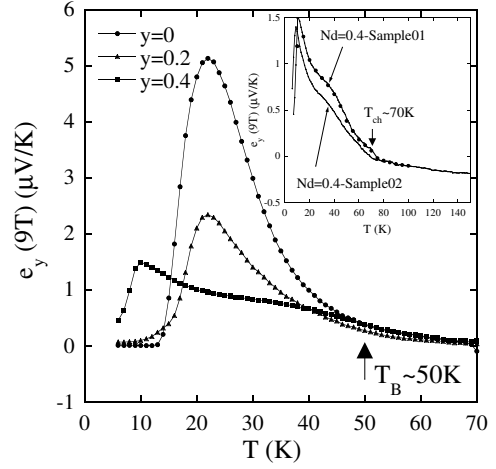


Figure 2: Nernst signal e_y at 9T for $\text{La}_{1.85-y}\text{Nd}_y\text{Sr}_{0.15}\text{CuO}_4$. T_B was determined as ref.[3]. Inset: Nernst signal e_y at 9T for $y=0.4$. To confirm reproducibility, we measured two different sample.

has been clearly observed below the charge order temperature T_{ch} (see the inset of Fig.2). This is crucial evidence that the static stripe order enhances the Nernst signal.

Based on the above results, we can define three characteristic temperatures: $T_{\text{onset}} > T_{ch} > T_B$. With decreasing temperature, the following scenario is expected at this stage: On the assumption that the enhancement of the Nernst signal is attributed to the effect of the stripe order at high temperatures, the fluctuation of the stripe order develops below T_{onset} , and then the static stripe order enhances the Nernst signal further at T_{ch} . With further decrease of temperature, a huge Nernst signal induced by the vortex flow is expected below T_B .

4. Conclusion

In order to investigate the effect of the charge (stripe) order on Nernst signal, we measured the temperature and magnetic-field dependences of the Nernst effect in Nd-doped $\text{La}_{2-x}\text{Sr}_x\text{CuO}_4$ single crystals with controlling the strength (stability) of the charge order. We found that the magnitude of Nernst signal drastically decrease with Nd doping below T_B , although T_{onset} does not change conspicuously, and that the Nernst signal is also enhanced at the charge ordered transition temperature T_{ch} . These results suggest that the stripe order as well as its fluctuation enhances the Nernst signal at high temperatures, whereas the stabilized stripe order tends to suppress the superconducting fluctuation and hence to reduce the Nernst signal at low temperatures.

References

- [1] Z. A. Xu et al., Nature, **406** (2000) 486.
- [2] R. Bel et al., Phys. Rev. Lett., **91** (2003) 066602.
- [3] Olivier Cyr-Choinière et al., Nature, **458** (2009) 743.
- [4] N. Ichikawa et al., Phys. Rev. Lett., **85** (2000) 1738.